

Absence of correlation between built-in electric dipole moment and quantum Stark effect in single InAs/GaAs self-assembled quantum dots

Weidong Sheng and Jean-Pierre Leburton

Beckman Institute for Advanced Science and Technology and Department of Electrical and Computer Engineering,
University of Illinois at Urbana-Champaign, Urbana, Illinois 61801

(Received 13 December 2002; published 19 March 2003)

We report significant deviations from the usual quadratic dependence of the ground-state interband transition energy on applied electric fields in single InAs/GaAs self-assembled quantum dots. While earlier works have used conventional second-order perturbation theory to claim a negative dipole moment in the presence of external electric field, we show that this theory fails to correctly describe the Stark shift for electric field below $F = 10$ kV/cm in high dots. Eight-band $\mathbf{k}\cdot\mathbf{p}$ calculations demonstrate that this effect is predominantly due to the three-dimensional strain field distribution which for various dot shapes and stoichiometric compositions drastically affect the hole ground state.

DOI: 10.1103/PhysRevB.67.125308

PACS number(s): 78.67.Hc, 31.15.Md, 73.21.La

I. INTRODUCTION

Self-assembled InAs/GaAs quantum dots (SAD's) are three-dimensional (3D) semiconductor nanostructures in which electrons and holes are completely confined along the three dimensions of space by the band gap difference between InAs and GaAs materials.¹ In these nanoscale systems, the determination of the electronic spectra of both particles represents a major challenge because of the low symmetry of the 3D confined nanostructures that take (truncated) pyramidal or lens shapes and are affected by the strong influence of strain due to the lattice mismatch between the InAs and GaAs crystals.² Experimentally, the difficulty of ascertaining the exact dot shape and the nonuniformity in size distribution resulting from the growth process are also a handicap.³ In this context, knowledge of the respective positions of electrons and holes can provide information on the confining potential experienced by both particles, which is of primary importance for fundamental⁴ as well as practical reasons.⁵

It has been recently argued that because of the nonhomogeneous stoichiometric composition of SAD's, resulting from atomic InAs-GaAs interdiffusion, the centers of mass of the ground-state electrons and holes are displaced from one another with the hole sitting above the electron, thereby inducing a built-in electric dipole oriented from the top to the base of the dot. This inverted electron-hole alignment⁶ has been obtained experimentally by assuming the usual linear relation between the electric dipole moment and the Stark shift in Stark effect spectroscopy on SAD's in p - i - n structures, i.e.,

$$E(F) = E_0 + pF + \beta F^2, \quad (1)$$

where E is the electron-hole ground-state transition energy, p is the built-in dipole moment, and β measures the polarization of the electron and hole states.

By estimating the electric field at which the maximum transition energy occurs, one can determine whether the structure has a positive (if that happens at positive fields) or negative (if otherwise) built-in dipole moment. This quadratic dependence is well known for quantum-well systems

and has been confirmed in nanocrystallite quantum dots.⁷ Recent theoretical works have made use of this linear relation to support the universality of the inverted alignment in SAD's.⁸

In this paper, we demonstrate that the linear relation between electric dipole moment and Stark shift as expressed in Eq. (1) is usually violated in SAD's because of the unique strain field distribution in the dot that strongly influences the rapidly varying confining potential for the holes. We show that this peculiar effect invalidates the conventional perturbation approach to establish the electric field dependence of the optical transitions in SAD's and leads to a reassessment of the direction and magnitude of the built-in electric dipole in the dots.

II. MODEL AND RESULTS

The system of SAD structures, containing both electrons and holes, can be well described by an eight-band strain-dependent $\mathbf{k}\cdot\mathbf{p}$ Hamiltonian,⁹ which reads

$$(\mathbf{H}_{k\cdot p}^0 + \mathbf{H}_{k\cdot p}^s + |e|Fz)\psi = E\psi. \quad (2)$$

Here $\mathbf{H}_{k\cdot p}^0$ and $\mathbf{H}_{k\cdot p}^s$ is the kinetic and strain-dependent part of the eight-band Hamiltonian,¹⁰ respectively, and $\psi = (\psi_1, \psi_2, \dots, \psi_8)$ is the envelop eigenvector. By using continuum elasticity theory, the strain tensor is calculated on a large grid of $150 \times 150 \times 150$ sites. The Hamiltonian is then solved by Lanczos algorithm. The same technique has been successfully applied to study few-particle effect¹¹ and optical transitions¹² in quantum dots and very good agreement with experiments has been achieved.

Figure 1 shows the calculated dependence of interband transition energies on electric fields for two SAD structures. Figure 1(a) illustrates the data for a $\text{In}_{0.8}\text{Ga}_{0.2}\text{As}$ dot with a constant composition throughout the structure. The pyramidal dot is 18 nm wide and 7.8 nm high, which is of similar size as that in the experiment of Fry *et al.*⁶ The electric field is applied vertically to the structure, pointing from the base to the top. For comparison, the corresponding experimental data are shown in the top-right inset.

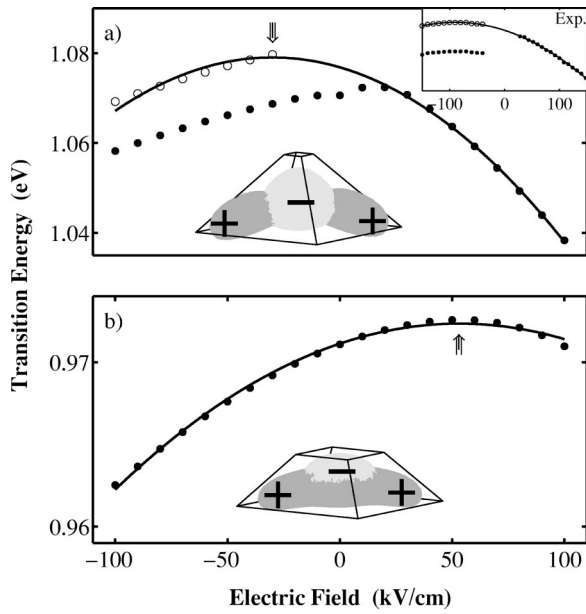


FIG. 1. Ground-state interband transition energies as a function of electric fields for two truncated pyramidal self-assembled quantum dots. Probability density isosurfaces of the ground states of electron (dark gray) and hole (light gray) are shown on a schematic view of the structure. The calculated points are shown in dotted lines. (a) The solid line is a fit to Eq. (1) using only the data at positive electric fields. The data at negative fields are shifted to the open dots by 11 meV to match the fitted curve. The top-right inset shows the corresponding experimental data taken from Ref. 6. (b) The solid line is a parabolic fit to all the data.

An clear deviation from the quadratic dependence of the transition energy on the electric field is obtained from our numerical simulations that show two distinct branches, one for roughly each field direction, merging at around zero field. It is interesting to notice that, if the data at negative electric fields are shifted upwards by 11 meV and if one ignores a few data points around zero field, one can easily fit the remaining data with a single parabola characterized by a maximum at around $F = -40$ kV/cm. In this case, according to Eq. (1), the displaced curve yields a negative built-in dipole (-14 Å) in spite of the fact that the center of mass of the electron state is above that of the hole state by 7 Å as shown in the lower inset, thereby achieving normal alignment.

This fitting procedure was adopted by Fry *et al.*⁶ to show the overall quadratic field dependence of the experimental transition energies (see upper right inset). The points marked with solid dots are the data measured from experiments. The authors shifted their data at negative fields to the position marked with open dots to match the curve fitting from their data at positive electric fields. With this procedure, they claimed a negative built-in dipole in the quantum dot structure. This experimental procedure was motivated by the fact that for *p-i-n* structures, the Stark shift in the transitions energies can only be measured under reverse biases. Consequently, given the asymmetric SAD shape and the fact that the Stark effect was measured for both field directions, two sets of samples, i.e., *p-i-n* and *n-i-p* structures, were needed in the experiment. Therefore, as far as a pyramidal shape,

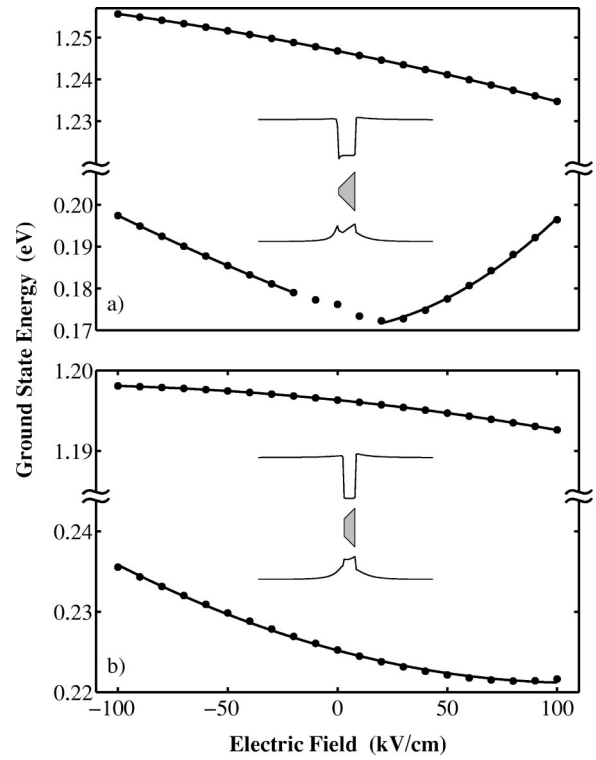


FIG. 2. Ground-state energies of electrons and holes as a function of electric fields for the two quantum dots shown in Fig. 1. The band diagrams are shown in the insets.

i.e., a SAD with a large height-base aspect ratio, is assumed, this fitting procedure may not have been suited for determining the exact direction of the electron-hole alignment in the SAD at equilibrium.

While the conventional perturbation theory fails for the pyramidal quantum dot, it makes a successful prediction of Stark shifts for another InAs SAD shape which is a largely truncated pyramid shown in Fig. 1(b), with the same base size, but is only 5.4 nm high. This SAD has smaller transition energies than the pyramidal structure because of its uniform InAs composition. Unlike the dot shown in Fig. 1(a), it has nearly perfect quadratic dependence of the transition energies on electric fields as strong as $F = \pm 100$ kV/cm. The parameter extracted from the fitting curve gives a positive built-in dipole of 4.57 Å which agrees well with the actual value 4.8 Å.

In Fig. 2, we show the electron and hole ground-state energies for the two structures as a function of electric fields. Electron energies for both structures are seen to have a linear profile with a slight bowing that can be well described by the usual quadratic dependence on the electric field, i.e.,

$$E_e(F) = E_e(0) + p_e F + \beta_e F^2, \quad (3)$$

in second-order perturbation theory. The hole state in the truncated structure exhibits a similar feature, and its energies can be well fitted with a parabola, i.e.,

$$E_h(F) = E_h(0) + p_h F + \beta_h F^2. \quad (4)$$

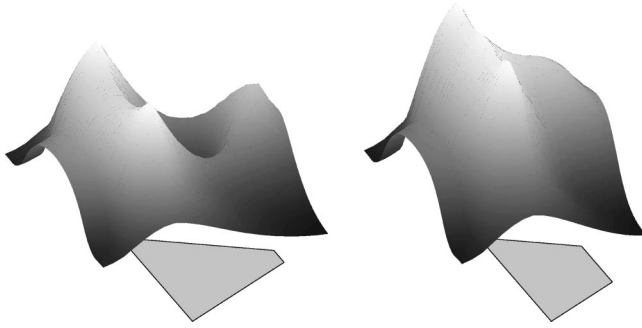


FIG. 3. Three-dimensional plots of strain distribution in a [100] plane across the center of quantum dots. Below the plots are the schematic views of cross sections of the structures.

Here $p_{e(h)}/|e| = \langle \psi_{e(h)} | z | \psi_{e(h)} \rangle$ is the center of mass of the electron (hole) state ψ_e (ψ_h) and $\beta_{e(h)}$ measures the polarization of the electron (hole) states. The correlation between the built-in dipole moment $p = p_e - p_h$ and the quantum Stark effect is then obtained by taking the difference between the electron and hole energies to reflect Eq. (1). In the pyramidal dot, however, a quadratic fitting for the whole field range is not possible, although the left and right branches of the spectrum could be fitted piecewise by two parabolas, respectively.

The different behavior of electron and hole energies is attributed to their respective band edge profiles shown in the insets of Fig. 2. In both SAD's, the conduction band edge is almost flat inside the dot with hard walls on the sides, which provides electrons a constant, strong confinement. Consequently, under the influence of external electric fields, electrons experience a smoothly varying confining potential inside the dot, which can be treated as a small perturbation with electron energies following the quadratic dependence given by Eq. (3). This type of behavior is also observed for holes in the truncated SAD structure [Eq. (4)].

In the pyramidal dot, the valence band edge exhibits a more complicated, double-triangular profile with the lower part extending from the SAD base to about two-thirds of the structure height, which effectively confines the ground hole state close to the bottom of the dot (see the inset in Fig. 1). Therefore, the holes are localized in a rapidly varying potential while the valence band edge changes abruptly close to the top of the structure. Hence, as vertical electric fields force the holes to move along the structure, they experience significantly different local confinement at different fields, which invalidates the perturbation approach as described in Eq. (1). This behavior is seen to occur at electric fields as low as $F = \pm 10$ kV/cm.

The rapidly varying confining potential which is responsible for the breakdown of the perturbation theory in the pyramidal structure is induced by the unique 3D strain field distribution within the SAD. Because the effect of other strain components on the valence bands is weaker, we concentrate on the biaxial component of the strain that affects mostly the valence bands.¹³ Figure 3 shows a 3D plot of the magnitude of biaxial strain along a [100] plane across the center of the quantum dots. It is pointed out that the biaxial

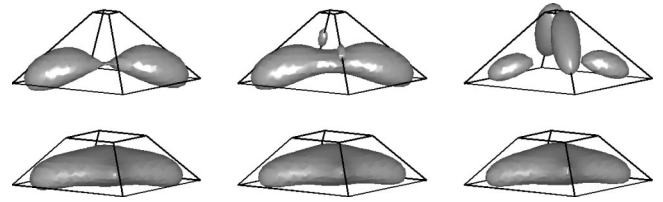


FIG. 4. Probability density isosurfaces of ground hole states at different electric fields, from left to right, -20 kV/cm, 10 kV/cm, and 20 kV/cm. Top panel: pyramidal dot [Fig. 1(a)]. Bottom panel: truncated dot [Fig. 1(b)].

component of strain takes negative value inside the dot that is under biaxial compression and positive value in the barrier that is under biaxial tension.

Despite the fact that the structural difference between the two dots results only from the truncation, both structures exhibit substantially different strain distribution. The biaxial strain distribution in the pyramidal dot shows rapid variation along the growth direction inside the structure, while the truncated dot exhibits a smoother profile. The strain field is so coherent that the tip of the pyramidal dot has a significant effect on the whole strain distribution.

In Fig. 4, we show the ground hole states at both negative and positive electric fields for the two structures. For the pyramidal structure of Fig. 1(a), the wave function at negative field $F = -20$ kV/cm looks similar to that at zero field except that it is localized closer to the dot bottom. At a positive field $F = 10$ kV/cm, the hole wave function develops a pair of small “wings” around the facet edges.¹⁴ Because of a strong local confinement imposed by the sharp triangular potential (see the band diagram inset in Fig. 2), the hole state could not extend into the upper half part of the structure as electron states do. At a stronger positive field $F = 20$ kV/cm, these wings even dominate over the other portions of the wave function.

III. DISCUSSION

The obvious asymmetric behavior of the ground hole states implies that the corresponding wave functions cannot be expanded to the first order in the electric field as

$$\psi_h(F) = \psi_h(0) + \phi_h F, \quad (5)$$

which would result in symmetric wave functions with respect to positive and negative electric fields for the whole range of electric fields. Instead, if we chose different values of the perturbation, ϕ_h , for negative and positive fields, respectively, it is possible to fit the hole energies with two parabolas (see Fig. 2).

In the truncated structure, the hole states are seen to have a different probability density distribution. The wave functions change very smoothly with the electric fields, because of a relatively flat valence band edge (see Fig. 2 inset). In addition, the lateral confinement close to the SAD top is also weaker compared with that in the pyramidal SAD as shown Fig. 1. Therefore, hole states behave coherently throughout

TABLE I. Calculated built-in dipole moments and their fitted values from the assumed quadratic dependence on the field for various quantum dot structures. All the lengths are expressed in nm. If not specified, all structures are homogeneous InAs/GaAs dots.

Size	Actual value	Fitted value
18×7.8^a	-0.31	N/A
18×7.8^b	0.70	-1.40
18×7.8	0.33	-1.23
18×9.0	0.36	-1.33
18×6.6	0.54	0.39
18×5.4	0.46	0.48

^aInhomogeneous InAs dot with two interdiffused monolayers, $\text{In}_{0.6}\text{Ga}_{0.4}\text{As}$ and $\text{In}_{0.8}\text{Ga}_{0.2}\text{As}$, in the bottom.

^bThe $\text{In}_{0.8}\text{Ga}_{0.2}\text{As}$ dot shown in Fig. 1(a).

the whole range of electric fields, exhibiting nearly perfect quadratic dependence of their eigen energies on electric fields.

Table I lists the actual and fitted values of dipole moments for several SAD's. All structures have the same base dimensions, but different heights or composition profiles. It should be stressed that the fitted values are obtained from the model data only for positive electric fields, i.e., the right branch of the spectrum. Except for the last structure, all values exhibit large discrepancy between the fitted curve and the model (calculated) data at negative fields. The first structure has a negative built-in dipole induced by the inhomogeneous diffusion,¹⁵ responsible for two bumps in the transition energy for positive and negative fields, which makes the fitting over a broad field range meaningless. This structure is similar to the SAD's investigated recently by Chen *et al.*¹⁶ where a negative dipole moment was extracted (the orientation of their field was opposite to ours) from a quadratic fitting over a smaller range of field ($-7.5 \text{ kV/cm} \leq F \leq 10 \text{ kV/cm}$), in good agreement with our data. The next three structures have homogeneous composition, and all exhibit positive dipoles. However, the fitted values for these structures are all nega-

tive. Therefore, it is a general feature of high pyramidal quantum dots with less than 25% truncation to exhibit erroneously a "negative" built-in dipole when fitted to the Stark shifts. The fourth structure has about 27% truncation with a dipole larger than those in the two previous dots. The corresponding fitted value is positive but is 30% smaller than the actual value. In the last structure, which is strongly truncated, the difference between the actual value and the fitted one becomes negligible.

Finally, we have calculated the excitonic correction to the interband transition energy by using the self-consistent Hartree method to take into account the electron-hole interaction. Although the shape of the electron wave function changes with the electric fields, the exciton energy is relatively insensitive to field variations since it only increases from 14.5 meV to 15.0 meV as the electric field varies from -50 kV/cm to 50 kV/cm . This variation is imperceptible on the plots in Fig. 1 and, consequently, does not change our conclusions.

IV. CONCLUSIONS

We have shown that the unique 3D strain field distribution is responsible for the breakdown of the linear dependence of the built-in electric dipole moment in the Stark shift in single SAD's. This effect is mostly noticeable in high SAD's where holes are mostly affected by rapidly varying components of the strain induced confining potential, which invalidates the second-order perturbation theory and results in an erroneous assessment of the respective positions of electrons and holes in the dots. While perturbation theory is expected to fail at strong electric fields, we point out that significant deviations from the usual Stark effect already occur at fields lower than $F = 10 \text{ kV/cm}$. For largely truncated or flat SAD's, the Stark shift retains its usual quadratic dependence on external fields.

ACKNOWLEDGMENTS

This work is supported by the Army Research Office, Grant No. DAAD 10-99-10129, and the National Computational Science Alliance, Grant No. ECS000002N.

¹D. Bimberg, M. Grundmann, and N. N. Ledentsov, *Quantum Dot Heterostructures* (Wiley, New York, 1998).

²I. Kegel, T. H. Metzger, A. Lorke, J. Peisl, J. Stangl, G. Bauer, J. M. García, and P. M. Petroff, *Phys. Rev. Lett.* **85**, 1694 (2000).

³Y. Ebiko, S. Muto, D. Suzuki, S. Itoh, K. Shiramine, T. Haga, Y. Nakata, and N. Yokoyama, *Phys. Rev. Lett.* **80**, 2650 (1998).

⁴D. Gammon, *Nature (London)* **405**, 899 (2000).

⁵D. G. Deppe and D. L. Huffaker, *Appl. Phys. Lett.* **77**, 3325 (2000).

⁶P. W. Fry, I. E. Itskevich, D. J. Mowbray, M. S. Skolnick, J. J. Finley, J. A. Barker, E. P. O'Reilly, L. R. Wilson, I. A. Larkin, P. A. Maksym, M. Hopkinson, M. Al-Khafaji, J. P. R. David, A. G. Cullis, G. Hill, and J. C. Clark, *Phys. Rev. Lett.* **84**, 733 (2000).

⁷S. A. Empedocles and M. G. Bawendi, *Science* **278**, 2114 (1997).

⁸J. A. Barker and E. P. O'Reilly, *Phys. Rev. B* **61**, 13 840 (2000).

⁹T. B. Bahder, *Phys. Rev. B* **41**, 11 992 (1990).

¹⁰C. Pryor, *Phys. Rev. Lett.* **80**, 3579 (1998).

¹¹L. Landin, M. S. Miller, M.-E. Pistol, C. E. Pryor, and L. Samuelson, *Science* **280**, 262 (1998).

¹²W. Sheng and J.-P. Leburton, *Appl. Phys. Lett.* **80**, 2755 (2002).

¹³T. B. Bahder, *Phys. Rev. B* **45**, 1629 (1990).

¹⁴C. Pryor, M.-E. Pistol, and L. Samuelson, *Phys. Rev. B* **56**, 10 404 (1997).

¹⁵W. Sheng and J.-P. Leburton, *Phys. Rev. B* **63**, 161301 (2001).

¹⁶Z. Chen, E.-T. Kim, and A. Madhukar, *Appl. Phys. Lett.* **80**, 2770 (2002).